



Studies in the Properties of Bending Elastic-Plastic Behavior of Some I Steel Beams

メタデータ	言語: eng 出版者: 室蘭工業大学 公開日: 2014-07-08 キーワード (Ja): キーワード (En): 作成者: 中村, 作太郎 メールアドレス: 所属:
URL	http://hdl.handle.net/10258/3500

Studies in the Properties of Bending Elastic-Plastic Behavior of Some I Steel Beams

Sakutaro Nakamura*

Abstract

In this paper the present writer stated that he pursued and found the behaviors and properties of bending elasticity and plasticity of some I steel beams simply and hinge-fixedly supported on both the ends, by giving two concentrated line loads on the span centre of each beam.

I. Introduction

The present writer made some I steel beams by use of H shaped steel of SS-41 and FCM-41 that are much applied as the members of bridges and architectural structures.

He pursued the extreme bending strength, the stress distribution and the elastic-plastic property within elastic limit and found some interest behaviors^{1)~3)} in some I steel beams having two concentrated line loads in the centre of span, simply and hinge-fixedly supported^{2)~4)} on both the ends.

Recently with the progress of science and the spread of its applied extent, the experiments^{5)~8)} of I steel beams are being actively carried out for the investigation^{9)~13)} of their elastic-plastic behaviors and the theoretical analyses are also being performed by using not only the elastic theory but the plastic theory and the elastic-plastic theory of I steel beams.

But it is very difficult to get the reasonable method of the theoretical analysis to consist with the actual elastic-plastic behavior on experiments, because the usual analytical formulae of elastic-plastic theory have the many problematic assumptions and are matched ill with the actual behavior.

In this study, the present writer pursued and discussed the bending elastic-plastic behaviors and many unknown properties of I steel beams simply and hinge-fixedly supported on both the ends.

II. Experiments of I-Beams on the Bending Elastic-Plastic Behavior

1. Experimental Apparatuses and Instruments

Universal testing machine: RH-100 type, max capacity-100 t; X-Y Recorder; Strain meter (Indicator): SM-4J type electric resistance static strain meter, DPM-E type electric resistance dynamic strain meter; Switch box SS-24J type; Strain

* 中 村 作太郎

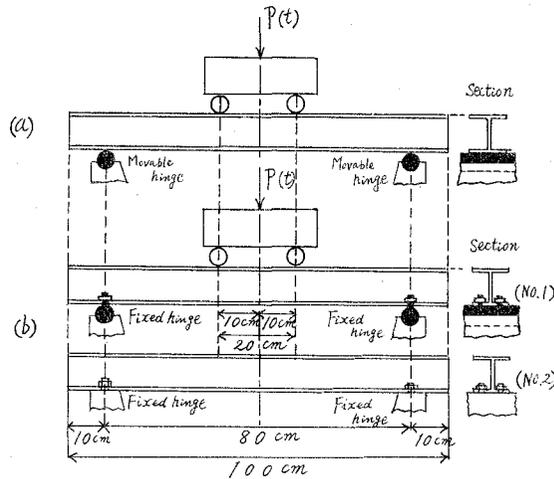


Fig. 2. Loaded and Supported States in the Experiments of I Steel Beams (Load: two symmetrically concentrated line-loads on the left and right of the span centre, Support: one kind of both simple supports and two kinds of both hinged and fixed supports No. 1 & No. 2).

Here, he observed, measured and calculated in detail the strain, the deflection and the stress intensity in the elastic and plastic behaviors of beam-models by making together use of the above-mentioned static and dynamic strain gauge, dial gauge and X-Y recorder.

Still more in this experiment he took specially a serious view of this plastic behavior of the vicinity of ultimate strength and the elastic-plastic behavior in the process from proportional limit to ultimate limit.

III. Theoretical Bending Solutions of I-Beams

1. Theoretical Elastic Solutions

The present writer adopted intact the assumptions of Bernoulli-Navier's law and Hook's one and some else assumptions used as ever in the bending elastic analysis of beams, and he introduced the next formulae.

$$\left. \begin{aligned} \varepsilon/y = 1/\rho = \phi, \quad M = \int_A \sigma y dA = EI\phi, \quad \sigma = E\varepsilon = Ey\phi, \\ M_y = EI\phi_y = \sigma_y S, \quad 0 < \phi < \phi_y \end{aligned} \right\} \quad (1)$$

Hereupon, ρ : Radius of curvature, ε : Strain, y : Vertical distance from neutral axis to any point, E : Modulus of elasticity, A : Sectional area, I : Geometrical moment of inertia, M : Bending moment within elastic limit, M : Yield bending moment, σ : Bending stress intensity within elastic limit, σ_y : Yield bending stress intensity, S : Section modulus, ϕ : Curvature within elastic limit, ϕ_y : Curvature in yield bending moment.

A. Theoretical Solutions of Simple Beams

Referring to Fig. 3, the present writer got the formulae of reaction, bending moment, shearing force, bending stress intensity, shearing stress intensity and deflection of the simple beams having two concentrated line loads in the centre of span as follows.

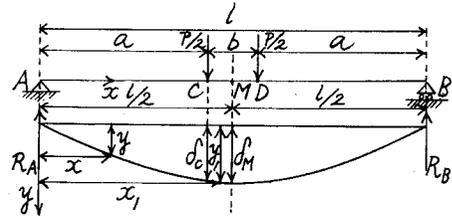


Fig. 3. Elastic Bending and Deflection of a simple Beam.

Reaction

$$R_A = R_B = P/2 ;$$

Bending moment

$$M = Px/2 \dots 0 \leq x \leq a, \quad M = P(l-x)/2 \dots (a+b) \leq x \leq l,$$

$$M_C = M_D = M_{\max} = Pa/2 ;$$

Shearing force

$$Q = P/2 \dots 0 \leq x \leq a, \quad Q = -P/2 \dots (a+b) \leq x \leq l ;$$

Bending stress intensity

$$\sigma = \pm My/I = \pm M/S$$

(+ : Tensile stress intensity, - : Compressive stress intensity)

Shearing stress intensity

$$\tau_{yz} = (Q/2ZI) \int_{y_1}^{y_0} y dF$$

(2)

Hereupon, y, z : Vertical and horizontal distance from a origin of the rectangular coordinate—the centre of sectional figure, dF : Area of minute section in the vertical distance y from a origin of the rectangular coordinate, y_0 : Vertical distance from a origin of the rectangular coordinate to each surface of the upper and lower flanges of section, y_1 : Vertical distance from a origin of the rectangular coordinate to the any point of τ_{yz} .

Bending deflection in the centre of span

$$\delta_M = (Pa/4EI)(a^3/3 - l^2/4)$$

Shearing deflection in the centre of span

$$\delta_Q = 2Pa(l-a)/lGA_w$$

(3)

Hereupon, G : Modulus of rigidity, A_w : Sectional area of web, l : Span length, P : Resultant of two concentrated line loads.

B. Theoretical Solutions of Hinge-Fixedly Supported Beams on Both the Ends

Hence referring to Fig. 4, the present writer showed the analytical formulae⁴⁾ of the reaction, the deflection angle, the deflection, the bending moment, the shearing force, the axial tensile force, the bending stress intensity and the shearing stress intensity in the hinge-fixedly supported beams having two symmetrically concentrated line loads and one side only load in their span centre part as (4)~(18).

In the case of beams having one left-side only load $P/2$ only referring to Fig. 4,

Reaction of the point A and B,

$$R_1 = (P/2)(1 - \epsilon), \quad R_2 = (P/2)\epsilon;$$

Deflection angle,

$$\varphi_1 = (Pl^2/8KI)f_1, \quad \varphi_2 = (Pl^2/8KI)f_2$$

However,

$$\left. \begin{aligned} f_1 &= \omega^{-2} \left[\frac{\sinh 2\epsilon\omega + \cosh 2\epsilon\omega - \sinh 2(2-\epsilon)\omega - \cosh 2(2-\epsilon)\omega}{(\sinh 4\omega + \cosh 4\omega - 1) + 1 - \epsilon} \right] \\ f_2 &= \omega^{-2} \left[\frac{\sinh 2(1-\epsilon)\omega + \cosh 2(1-\epsilon)\omega - \sinh 2(1+\epsilon)\omega - \cosh 2(1+\epsilon)\omega}{(\sinh 4\omega + \cosh 4\omega - 1) + \epsilon} \right], \\ 0 &< \epsilon < +1 \end{aligned} \right\} \quad (4)$$

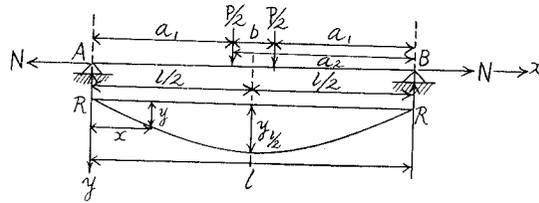


Fig. 4. Elastic Bending and Deflection of a Hinge-Fixedly Supported Beam.

In the case of beams having two symmetrically concentrated line loads ($P=P/2+P/2$), the reaction, the deflection angle, the deflection and the bending moment are as follows.

Reaction

$$R = R_1 + R_2 = P/2$$

Deflection angle

$$\varphi = (\varphi_1 + \varphi_2) = (Pl^2/8KI)(f_1 + f_2)$$

Calculating formulae of deflections in the any point,

$$y = (1/\xi) \left\{ (P/2N) (\xi x - \sinh \xi x) + (\varphi_1 + \varphi_2) \sinh \xi x \right\} \dots 0 \leq x \leq a$$

$$\left. \begin{aligned}
 y &= (1/\xi) \left[(P\varepsilon/2N) \{ \xi x - \sinh \xi x + \xi(l-x) - \sinh \xi(l-x) \} \right. \\
 &\quad \left. + \varphi_2 \{ \sinh \xi(l-x) + \sinh \xi(l-x) \} \right] \cdots a \leq x \leq (a+b) \\
 y &= (1/\xi) \left[(P/2N) \{ \xi(l-x) - \sinh \xi(l-x) + (\varphi_1 + \varphi_2) \sinh \xi(l-x) \} \cdots \right. \\
 &\quad \left. (a+b) \leq x \leq l \right]
 \end{aligned} \right\} (6)$$

Calculating formulae of bending moments in the any point,

$$\left. \begin{aligned}
 M_x &= (1/\xi) \sinh \xi x \{ P/2 - N(\varphi_1 + \varphi_2) \} \cdots 0 \leq x \leq a \\
 M_x &= (1/\xi) \{ \sinh \xi x + \sinh \xi(l-x) \} \{ (P/2)\varepsilon - N\varphi_2 \} \cdots a \leq x \leq (a+b) \\
 M_x &= (1/\xi) \sinh \xi(l-x) \{ P/2 - N(\varphi_1 + \varphi_2) \} \cdots (a+b) \leq x \leq l
 \end{aligned} \right\} (7)$$

Deflection in the centre of span,

$$y = (1/\xi) \left[(P/2N) \{ \xi(l/2) - \sinh \xi(l/2) \} + (\varphi_1 + \varphi_2) \sinh \xi(l/2) \right] \quad (8)$$

Bending moment in the centre of span,

$$M_{l/2} = (1/\xi) \sinh \xi(l/2) \{ P/2 - N(\varphi_1 + \varphi_2) \} \quad (9)$$

Shearing force in the any point,

$$\left. \begin{aligned}
 Q &= P/2 \cdots 0 \leq x \leq a \\
 Q &= -P/2 \cdots (a+b) \leq x \leq l
 \end{aligned} \right\} (10)$$

In the case of beams having one side only concentrated line load, the calculating equation of the axial tensile force N is as follows.

$$\left. \begin{aligned}
 &\sum_{n=1}^2 (1/k_n^4) 2R_n \varphi_n a_n^5 KI (\sinh 2k_n/2k_n + \sinh k_n/k_n - \cosh k_n - 1) \\
 &- \sum_{n=1}^2 (1/k_n^6) R_n^2 a_n^7 (\sinh 2k_n/2k_n + 2 \sinh k_n/k_n - 2 \cosh k_n - 1) \\
 &- \sum_{n=1}^2 (1/k_n^2) \varphi_n^2 a_n^3 K^2 I^2 (\sinh 2k_n/2k_n - 1) - 4IK^2 I^3/4 = 0
 \end{aligned} \right\} (11)$$

Moreover, the above-mentioned equation can be shown also by the next equation.

$$\left. \begin{aligned}
 &\sum_{n=1}^2 \left\{ 2KIR_n \varphi_n a_n^5 f_1(k_n) - R_n^2 a_n^7 f_2(k_n) - K^2 I^2 \varphi_n^2 a_n^3 f_3(k_n) \right\} = 4IK^2 I^3/A \\
 \text{However,} \\
 &f_1(k_n) = (1/k_n^4) (\sinh 2k_n/2k_n - 1 - \cosh k_n + \sinh k_n/k_n) \\
 &f_2(k_n) = (1/k_n^6) (\sinh 2k_n/2k_n + 2 \sinh k_n/k_n - 2 \cosh k_n - 1) \\
 &f_3(k_n) = (1/k_n^2) (\sinh 2k_n/2k_n - 1)
 \end{aligned} \right\} (12)$$

Then this axial tensile force N of a beam having two symmetrically concentrated line loads ($P = P/2 + P/2$) in the span centre part is twice as large as

that of a beam having one side only load ($P/2$) in the same part.

Moreover,

Bending stress intensity

$$\sigma = \pm My/I = \pm M/S$$

(+ : Tensile stress intensity, - : Compressive stress intensity)

Shearing stress intensity

$$\tau_{yz} = (Q/2ZI) \int_{y_1}^{y_0} y dF$$

(13)

2. Elastic-Plastic Bending Analytical Solutions^{(2), (9), (12), (13)}

A. Theoretical Assumptions for Elastic-Plastic Bending Analysis of Beams

The assumptions of analysis in the elastic-plastic bending behavior of beams have been backed up properly by many experiments and may be shown as follows.

- i. The strain is proportionate to the distance from the neutral axis.
- ii. The physical relation of stress-strain is elastic before the stress intensity σ_y in the static yield point and after that it becomes plastically flowing without any restriction under the constant stress intensity σ_y .
- iii. The physical relation of stress-strain in the compressive side is the same as the one in the tensile side.
- iv. Assuming that the deformation is microscopic, the curvature of a bended beam is approximately formularized by the twice differentiated expression.

In the plastic bending behavior of beams, the assumption of i. is well applied in the distribution of strain and the ones of ii. and iii. are likewise applied in the distribution of stress.


B. Theoretical Solutions of Simply Bended I-Beams⁽¹²⁾

Fig. 5 (a) shows that the yieldings begin with the heads of both flanges and the outside parts of both flanges become the plastic domain.

Then,

$$\begin{aligned} M &= 2 \int_{y_0}^{d/2} \sigma_y y b dy + 2 \int_{d/2}^y (\sigma_y/y_0) y b y dy \\ &\quad + \int_0^{d_w/2} (\sigma_y/y_0) y w y dy + 2 \int_0^{d_w/2} (\sigma_y/y_0) y w y dy \\ &= \sigma_y (bd^2/4 - by_0^2/3 - bd_w^3/12y_0 + wd_w^3/12y_0) \\ &= \sigma_y b (d^2/4 - \sigma_y^2/3E^2\phi^2) - (E\phi d/2) (S - bd^2/6) \end{aligned} \quad (14)$$

Hereupon, b : Width of flange, t : Thickness of flange, w : Thickness of web plate, d_w : Depth of web plate, d : Depth of I-beam, I : Geometrical moment of inertia of I-beam = $bd^3/12 - bd_w^3/12 + wd_w^3/12$, S : Section modulus of I-beam = $I/(d/2)$, y_0 : Depth of the elastic domain = $\sigma_y/E\phi$

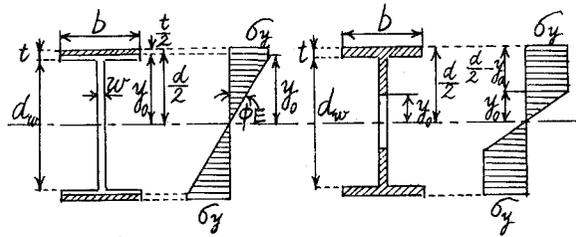

(a) Yielding within Flanges (b) Yielding within Web Plate

Fig. 5. Elastic-Plastic Bending of a I-Beam.

Moreover,

$$M/M_y = (bd^2/4S) \left\{ 1 - (1/3) (\phi_y/\phi)^2 \right\} + (\phi/\phi_y) (1 - bd^3/6S) \quad (15)$$

The formula (15) is applied for the extent that the outside parts of both flanges begin to yield and the total parts of both flanges yield perfectly, namely—the extent of $1 < \phi/\phi_y < (d/2)/\{(d/2)-1\}$.

Next, referring to Fig. 5 (b) the present writer considers on the extent that totally both flanges yield perfectly, the web plate begins to yield and the inner parts of a web plate become plastic.

$$\left. \begin{aligned} M &= 2 \int_{d_w/2}^{d/2} \sigma_y b y dy + 2 \int_{y_0}^{d_w/2} \sigma_y w y dy + 2 \int_y^{y_0} (\sigma_y/y_0) y w y dy \\ &= \sigma_y (bd^2/4 - bd_w^2/4 + wd_w^2/4) - \sigma_y w y_0^2/3 \end{aligned} \right\} \quad (16)$$

The plastic section modulus Z of a I-beam are divided into three pieces Z_1 , Z_2 and Z_3 as Fig. 6.

As every element is the rectangular section, the values of Z_1 , Z_2 and Z_3 are shown as follows.

$$Z_1 = bd^2/4, \quad Z_2 = bd_w^2/4, \quad Z_3 = wd_w^2/4$$

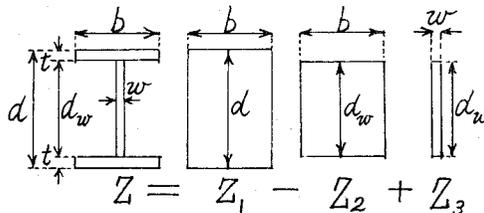


Fig. 6. Plastic Section Modulus of a I-Beam.

Then,

$$M = \sigma_y (Z - w y_0^2/3) = \sigma_y \left\{ Z - (w/3) (\sigma_y^2/E^2 \phi^2) \right\} \quad (17)$$

However,

$$0 < y_0 < d_w/2$$

$$\left. \begin{aligned} M/M_y &= Z/S - (\omega/3) (\sigma_y^2/E^2 \phi^2 S) \\ &= Z/S - (\omega d^2/12S) (\phi_y/\phi)^2 = f - (\omega d^2/12S) \end{aligned} \right\} (18)$$

However,

$$(d/2) / \left\{ (d/2) - 1 \right\} < \phi/\phi_y < \infty$$

In the formula (18),

$$M_y = \sigma_y S = EI \phi_y \quad (19)$$

or,

$$\sigma_y = E \phi_y (d/2)$$

In the case of a I-section, the moment of a beam goes rapidly near the ultimate moment M_y than the case of a rectangular section.

Namely, the excess strength of a I-beam decreases rapidly after the yielding of its total, not only outside surface, flanges.

C. Theoretical Solutions of a Bended I-Beam with Axial Force¹²⁾

Referring Fig. 7, the present writer shows explanatively the theoretical formulae of plastic moments and stress intensities of I-beams.

By the value's ratio of the bending moment M and the axial force N , the behavior of I-beams is classified in the two cases that the neutral axis exists within the web plate or the flange.

i. The Case of a I-Beam with Neutral Axis Existing within Its Web Plate

From the stress distribution of the ultimate moment of Fig. 7,

$$\left. \begin{aligned} N &= \int_A \sigma dA = \sigma_y (2\omega y_0) \\ N_{yc} &= \sigma_y (A_f + A_w) \end{aligned} \right\} (20)$$

However, N_{yc} : Yielding axial force

Therefore,

$$N/N_{yc} = 2y_0/d_w (1 + A_f/A_w) \quad (21)$$

And the plastic moment M_{pc} of a beam with the axial force is shown as the next formula.

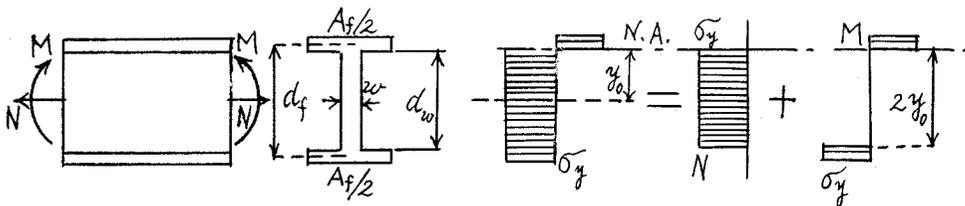


Fig. 7. I-Beam with Bending Moment and Axial Force, Case I (Neutral Axis within Web Plate).

$$\left. \begin{aligned} M_{pc} &= \int_A \sigma_y dA = \sigma_y (A_f d_f / 2 + A_w d_w / 4 - b y_0^2) \\ M_p &= \sigma_y (A_f d_f / 2 + A_w d_w / 4) \end{aligned} \right\} \quad (22)$$

However, M : Common plastic moment of simple beam

Thereupon,

$$M_{pc} = M_p - \sigma_y b y_0^2$$

or,

$$M_{pc} / M_p = 1 - b y_0^2 / Z \quad (23)$$

By putting y_0 of the formula (21) into (23), the next formula is got.

$$M_{pc} / M_p = 1 - \left\{ (N / N_{pc}) (1 + A_f / A_w) \right\}^2 \left\{ 1 / (1 + 2 A_f d_f / A_w d_w) \right\} \quad (24)$$

Presuming from the elastic theory, the elastic-plastic stress intensity of a I-beam with the plastic section modulus Z is shown as the next formula.

$$\sigma = N_y / (A_f + A_w) \pm M_{pc} / Z \quad (25)$$

ii. The Case of a I-Beam with Neutral Axis Existing within Its Flange

The neutral axis movement of a I-beam grows larger in proportion as the magnitude of its axial force and its neutral axis goes on moving within its flange at last.

The formula (24) or (25) may be applied when its neutral axis exists within its web plate, but the special relation of the bending moment and the axial force is induced from the stress distribution of Fig. 8.

Then, from Fig. 8,

$$N = \sigma_y \left[A_w + A_f \left\{ 1 - 2\Delta / (d - d_w) \right\} \right], N_{yc} = \sigma_y (A_w + A_f) \quad (26)$$

Therefore,

$$N / N_{yc} = \left[1 + (A_f / A_w) \left\{ 1 - 2\Delta / (d - d_w) \right\} \right] / (1 + A_f / A_w) \quad (27)$$

$$M_{pc} = (\sigma_y A_f / 2) 2\Delta (d - \Delta) / (d - d_w), \quad M_p = \sigma_y (A_f d_f / 2 + A_w d_w / 4)$$

Therefore,

$$M_{pc} / M_p = \left\{ 2\Delta (d - \Delta) / (d - d_w) \right\} / (d_f + A_w d_w / 2 A_f) \quad (28)$$

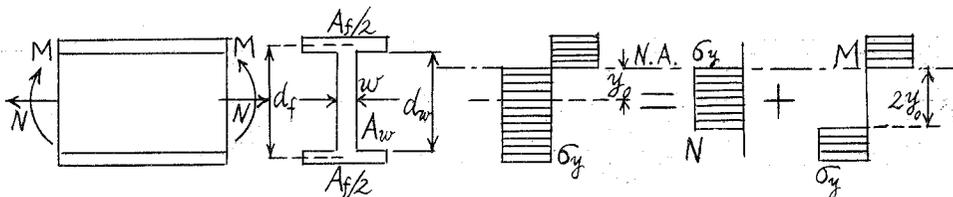


Fig. 8. I-Beam with Bending Moment and Axial Force, Case II (Neutral Axis within Flange).

As Δ is smaller than d ,

$$d - \Delta \cong d$$

Therefore,

$$M_{pc}/M_p = (2\Delta/d - d_w) \left\{ 2 / (1 + d_w/d + A_w d_w / A_f d) \right\} \quad (29)$$

Eliminating Δ from the formulae (27) and (29),

$$M_{pc}/M_p = \left[(2d/d_w) / \left\{ 1 + (1 + d/d_w) (A_f/A_w) \right\} \right] \\ \times \left[A_f/A_w - \left\{ (N/N_{yc}) (1 + A_f/A_w) - 1 \right\} \right] \quad (30)$$

Or, applying the plastic section modulus Z and the total sectional area A ,

$$M_{pc}/M_p = (A/2Z) (1 - N/N_{yc}) \left\{ d - (A/2b) (1 - N/N_{yc}) \right\} \quad (31)$$

Generally it may be certified that the average value of d_f/d_w or d/d_w in I steel beams is nearly 1.05 or 1.10 and these values are applied in the calculation of I steel beams.

Then when the axial force N is zero, M_{pc} becomes equal to M_p , and when the bending moment M_p is zero, N becomes properly equal to N_p .

IV. Comparison of Experimental Results and Theoretical Values

Fig. 9, Fig. 10, Fig. 11 and Fig. 12 show severally the distribution curves of sectional stress intensities within a elastic limit, the Load-Strain Curves of the elastic and plastic behaviors at the principal points of the upper and lower flanges and the web plate and the Load-Deflection Curves of the elastic and plastic behaviors at the centre of span.

V. Conclusion

1. The present writer could certify that from the view point of the distribution curves of sectional stress intensities, the Load-Strain Curves of the principal points and the Load-Deflection Curves of the span centre, every experimental result agrees almost to its corresponding theoretical value and that the elastic beam theory is generally right.

2. He could also confirm that in the plastic domain and the special extent of the elastic-plastic shifting process the experimental Load-Strain Curves of the principal points and the experimental Load-Deflection Curves of the span centre get both approximately near their corresponding theoretical ones, but he felt keenly that the elastic-plastic beam theory are considerably imperfect judging from the comparison of theoretical rough values and experimental scrupulous results.

3. It was confirmed that the experimental process from the yielding load to

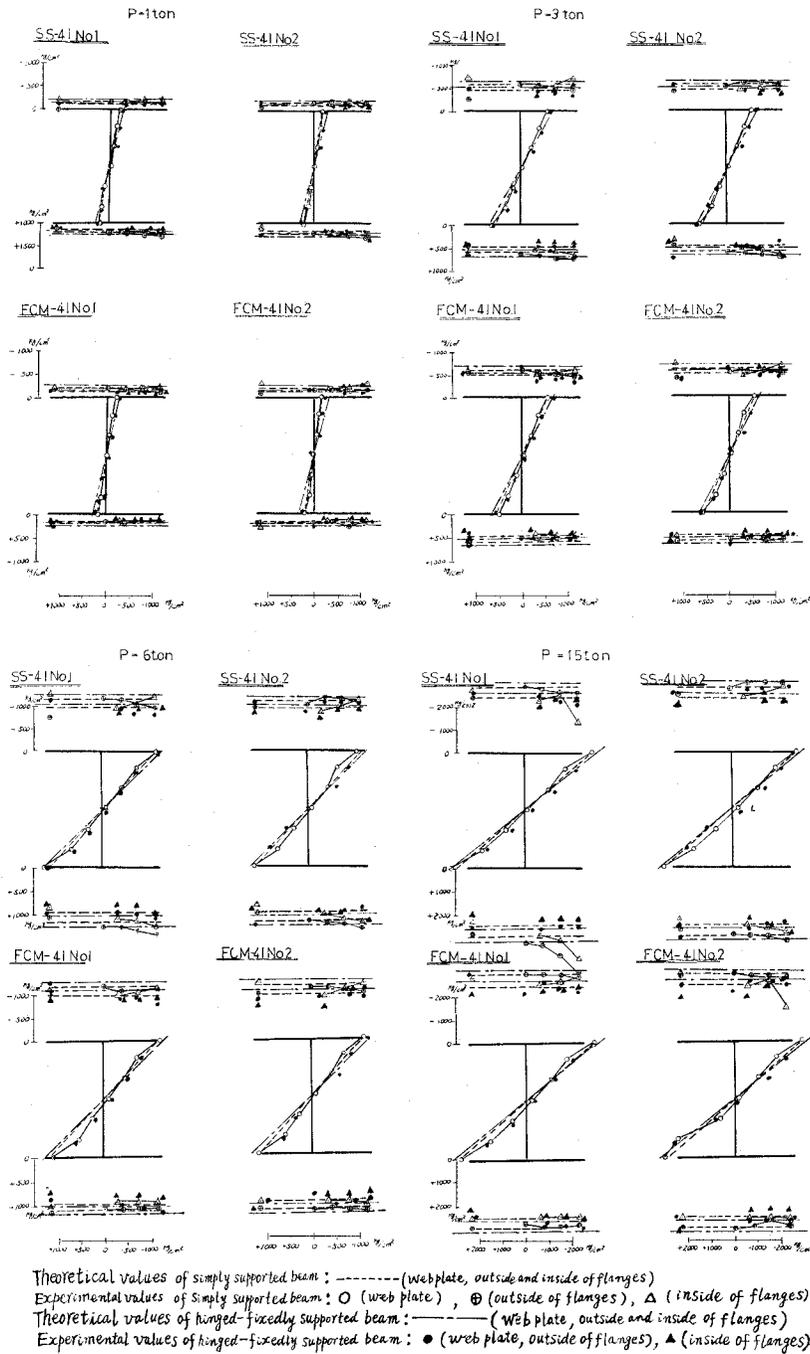


Fig. 9. Distributions of Bending Stress Intensities σ_x in the Elastic Domain of I Steel Beams (Measured Points $x=l/2$, Loads $P=1\text{ t}, 3\text{ t}, 6\text{ t}, 15\text{ t}$).

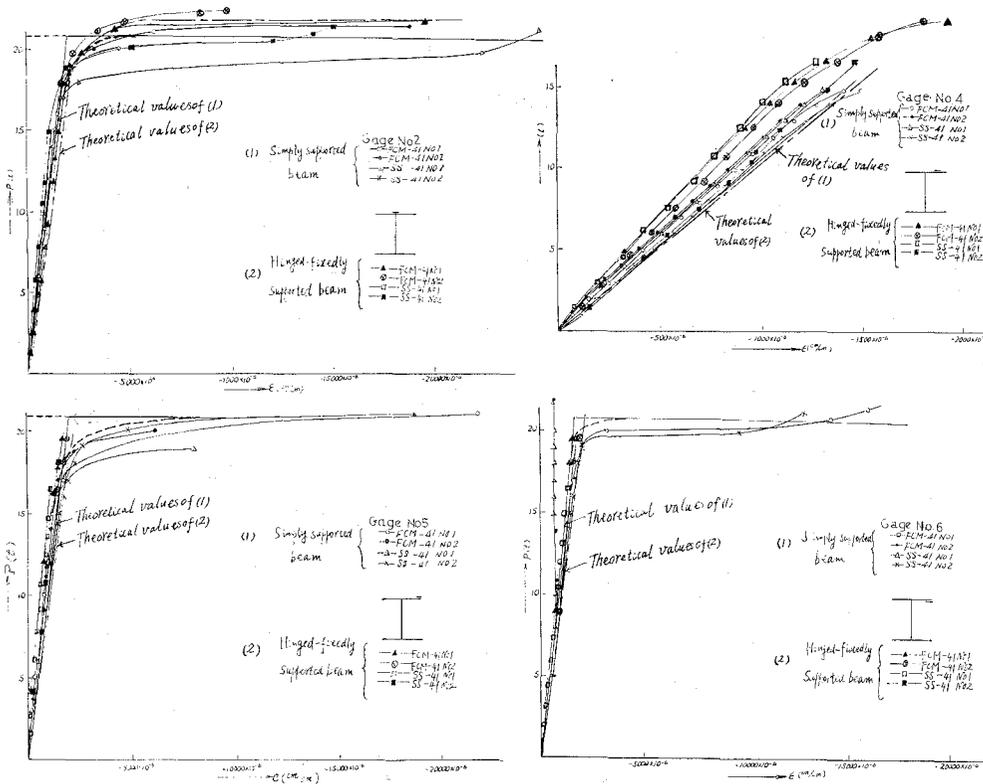


Fig. 10. Load-Strain Curves on the Principal Points (No. 2, 4, 5, 6) of Upper Flanges in the Elastic and Plastic Behaviors of I Steel Beams (Measured Points $x=l/2$).

the ultimate load approaches indicatively to the corresponding theoretical process and the present writer could also confirm that the ultimate strengths of I steel beams agree nearly to the ones of steel materials in the standard test⁽¹⁴⁾.

4. It was also certified that the distribution curves of sectional stress intensities and the Load-Strain Curves of the principal points in the FCM-41 steel-mounted I-beams are more excellent than those in the SS-41 steel-mounted ones.

5. The present writer could lastly confirm that the magnitude of an axial tensile force N in the I steel beams hinge-fixedly supported on both the ends changes remarkably by the ratio of a sectional area A to a span $l—A/l$, namely— N decreases so much more as A/l increases.

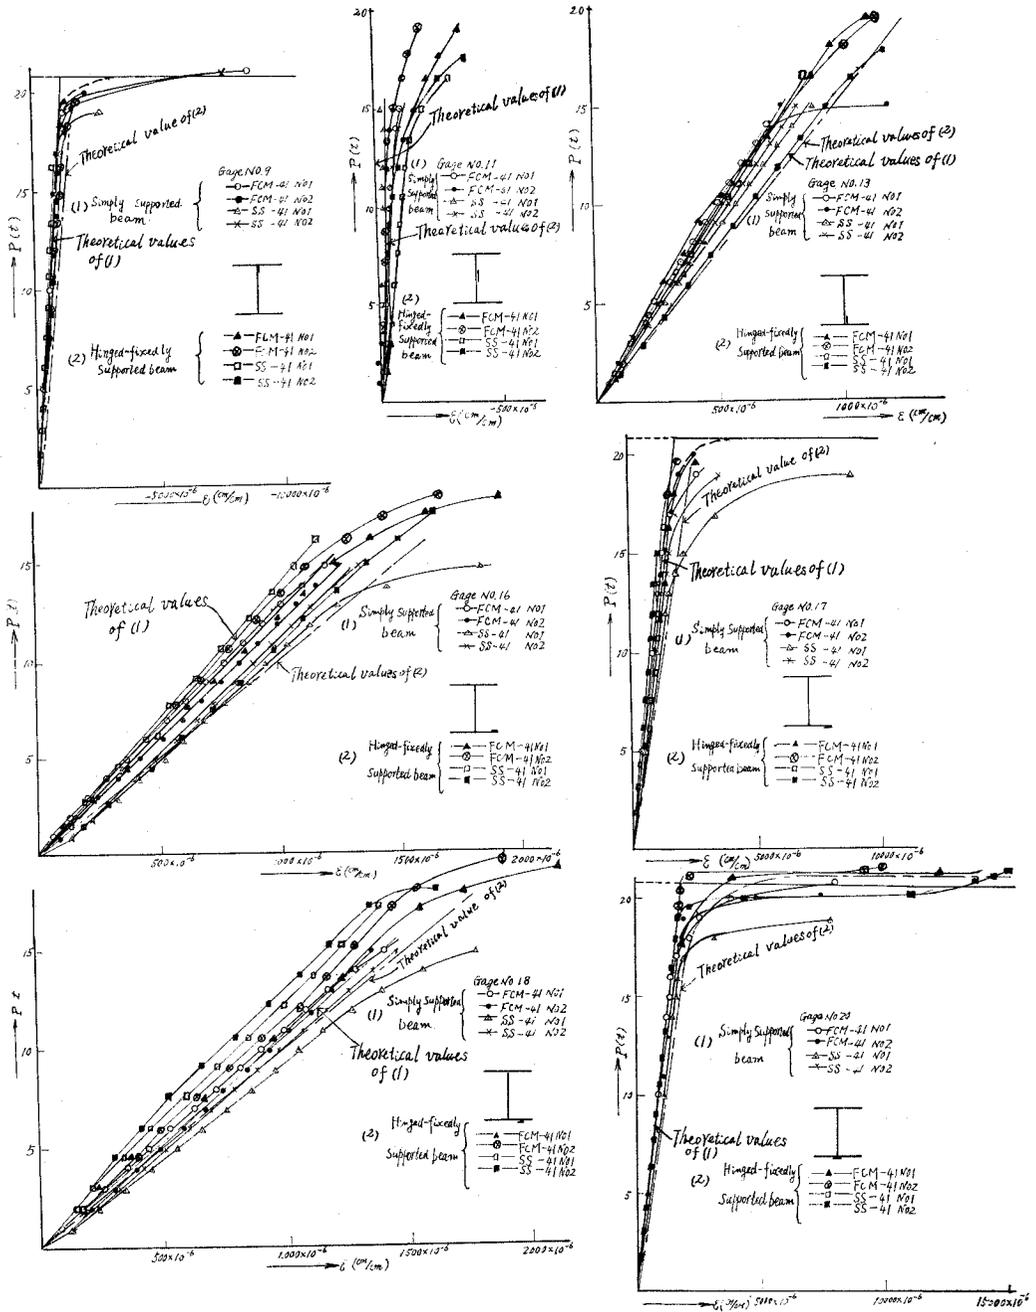


Fig. 11. Load-Strain Curves on the Principal Points (No. 9, 11, 13, 16, 17, 18, 20) of Lower Flanges and Web Plates in the Elastic and Plastic Behaviors of I Steel Beams (Measured Points $x=l/2$).

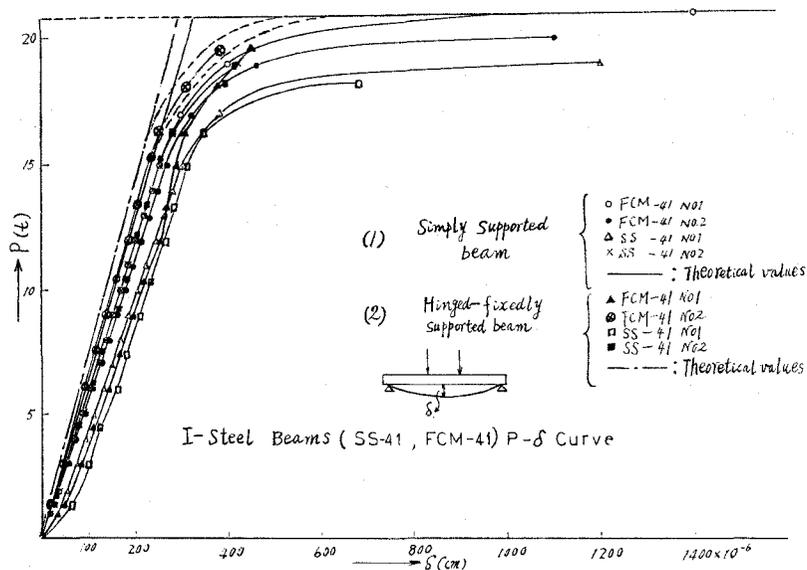


Fig. 12. Load-Deflection Curves of the Span Centre in the Elastic and Plastic Bending-Behaviors of I Steel Beams.

Acknowledgement

The present writer is obliged to express his sincere thanks to his assistant, Mr. Masao Shimura and some students in the Civil Engineering Department of Muroran Institute of Technology, for their kind cooperation in this study.

(Received May 19, 1970)

References

- 1) S. Nakamura and M. Shimura: The Collection of Summaries in the 24th Annual Science Lecture Meeting of Japan Society of Civil Engineers, I-13, 33 (Tokyo, 1969).
- 2) S. Nakamura and M. Shimura: Memoirs in the 16th Bridge and Structural Engineering Lecture Meeting of the Japan Science Council Committee, the Japan Society of Civil Engineers and the Architectural Institute of Japan, 31 (Tokyo, 1969).
- 3) S. Nakamura and M. Shimura: Memoirs in the Hokkaido Branch of the Japan Society of Civil Engineers, II-1, 117 (Sapporo, 1970).
- 4) S. Nakamura: Memoirs of the Muroran Institute of Technology 2, (2), 151 (Muroran, 1956).
- 5) R. W. Frost and C. G. Schilling: Journal of the Proceedings of the American Society of Civil Engineers, ST3, 55 (New York, 1964).
- 6) A. Chajies: Journal of the Proceedings of the American Society of Civil Engineers, ST6, 1549 (New York, 1968).
- 7) K. Basler and B. Thürlimann: Journal of the Proceedings of the American Society of Civil Engineers, ST 6, 153 (New York, 1961).
- 8) H. A. Sawyer: Journal of the Proceedings of the American Society of Civil Engineers,

- ST 8, 43 (New York, 1961).
- 9) P. G. Hodge: The Plastic Analysis of Structures, joint trns. M. Kuranishi and five others, Korona Company, 11 (Tokyo, 1961).
 - 10) Н. И. Безухов: Elasticity and Plasticity, trans. T. Sato, Nikkan Engineering Newspaper Office, 301 (Tokyo, 1956).
 - 11) A. M. Freudenthal: The Inelastic Behavior of Engineering Materials and Structures, joint trans. K. Yanagishima and two others, Korona Company, 219 (Tokyo, 1961).
 - 12) Y. Fujita and two others: The Plastic Design Method, Morikita Press Company, 15 (Tokyo, 1961).
 - 13) H. Udoguchi: Strength of Materials (Last Volume), the Japan Society of Mechanical Engineers, 479 (Tokyo, 1963).
 - 14) Fuji Iron-Manufacturing Company: Fuji Cor-Ten Bridge Manual for the Weathering High Tension Steel, Fuji Iron-Manufacturing Company, 3 (Tokyo, 1967).